



DOI: 10.18720/MCE.92.9

CO₂ curing of hydrated lime modified pervious concretes

H. Rahmani*, **M. Montazer Gheib**

University of Zanjan, Zanjan, Iran

* E-mail: hrahmani@znu.ac.ir

Keywords: carbonation curing, CO₂ absorption, hydrated lime, pervious concrete

Abstract. This paper presents the effect of carbonation curing on the properties of hydrated lime modified pervious concretes. Also, CO₂ absorption capacity (COAC) of the mixtures was investigated to more explanation of the results. Three mix designs containing of 0, 15 and 30 % of hydrated lime were considered. Water to cement ratio, cementitious material content, inner pressure of the chamber and workability of the mixtures were kept constant. Concrete samples were cured in the CO₂ chamber and then the conducted experiments were performed and the results compared with the results of moist cured concretes. The results showed a significant increase in the mechanical properties of the concretes at the initial time of CO₂ curing. Carbonation reactions were approximately stopped after 12 hours of CO₂ curing in which the concrete properties after 12 hours of CO₂ curing were closed together. Also, COAC of the mixtures increased by increasing hydrated lime substitution.

1. Introduction

Carbon dioxide (CO₂) as one of the major greenhouse gases causes world climate changes. It has been estimated that the CO₂ emission will be increased during the next decades, nevertheless the CO₂ concentration in the atmosphere is higher than the maximum allowable concentration. Therefore, sequestration of CO₂ is essential to reduce its concentration in the atmosphere [1]. Geological sequestration of CO₂ in oceans and other fluid storages such as aquifers and oil wells are in progress [2]. However, some minerals can react chemically with CO₂ and produce carbonates. Calcium and Calcium-silicate minerals can properly convert CO₂ to calcium carbonates, but they are rarely found in the nature. However, popular synthetic materials such as Portland cement as a calcium-silicate material and hydrated lime as a calcium material can be efficiently used to mineralize CO₂ to calcium carbonate. This process of direct sequestration of CO₂ is called carbonation curing or CO₂ curing of cement-based materials, where appropriate curing provides a proper mineralization of CO₂ [1, 3–5]. Since the pervious concretes are more porous, it is estimated that the mineralization of CO₂ is simply completed. Therefore, CO₂ curing of the hydrated lime modified pervious concretes is the main object of this study.

1 kg cement can absorb 0.5 kg CO₂ to form 1.5 kg silica gel and calcium carbonates [1]. Reactivity of calcium silicates and mineral admixtures with CO₂ were systematically studied by the researchers [6–9]. Carbonation curing or CO₂ curing improves compressive strength, surface hardness and durability of non-reinforced cement-based products [10–12]. However, the carbonation process reduces the pH of concrete and initiate the corrosion of reinforcing bars in concrete [13–16]. Therefore, non-reinforced concretes have a great potential to friendly absorb CO₂. This would be appreciated by the manufacturers of cement-based materials when CO₂ curing is accelerated by increasing of curing temperature, pressure, CO₂ concentration, porosity of concrete and water to cement ratio and also by adjusting the proper relative humidity (RH) of the chamber [17–19]. In addition, cement replacement materials and novel concretes have been investigated to absorb CO₂ in the last decades [9, 12, 17, 19–22]. For instance, Monkman and Shao have used slag-cement concrete to bind CO₂ [12] and Kou et al. and Zhan et al. have investigated CO₂ curing of concretes prepared with recycled aggregates [19–21]. Also, CO₂ curing of self-compacting and lightweight concretes have been systematically investigated by Shamsad et al. and Shi and Wu, respectively [17, 22]. Nevertheless several researchers have investigated carbonation curing of concretes including novel ones, but there is a limit research on CO₂ curing of pervious concretes [23, 24]. For instance, Hasegawa has investigated static and dynamic carbonation curing of pervious concrete using ordinary Portland cement and Portland limestone cement and concluded that the early carbonation curing (2 hours for static and 30 minutes for dynamic carbonation curing) significantly improves the

Rahmani, H., Montazer Gheib, M. CO₂ curing of hydrated lime modified pervious concretes. Magazine of Civil Engineering. 2019. 92(8). Pp. 106–114. DOI: 10.18720/MCE.92.9



Рахмани Х., Монтазер Гейб М. Насыщение CO₂ гидратированного известью модифицированного проницаемого бетона // Инженерно-строительный журнал. 2019. № 8(92). С. 106–114. DOI: 10.18720/MCE.92.9



This work is licensed under a CC BY-NC 4.0

physical and mechanical properties of the concretes [23]. Sidhu indicated that the pervious concretes with 12 hours of CO₂ curing showed the highest compressive strength and the lowest porosity when they were compared with other curing regimes [24].

The major chemical reactions of CO₂ curing of cement-based materials such as concrete are given by Equations (1) and (2) [1, 5, 9, 17]. Also, CO₂ reacts with Ca(OH)₂ and forms CaCO₃, where the rate of reactions depends on the rate of CO₂ diffusion [5].



Nevertheless a lot of researches have been conducted on the properties and the durability of pervious concretes including modified ones [25–30], but carbonation curing of pervious concretes has not been completely investigated. Therefore CO₂ curing of pervious concretes is investigated in this study. Also, since hydrated lime can react with CO₂ and accelerate the CO₂ curing process of the concretes, substitution of hydrated lime is considered in the mixtures up to 30 % of cement to absorb more CO₂. It is predicted that the properties of pervious concretes will diminish in case of more substitution of hydrated lime because of low content of cement in the mixtures. Consequently, main objects of this study are the increasing of CO₂ absorption capacity and the improvement of mechanical and physical properties of pervious concretes simultaneously by means of carbonation curing.

2. Methods

2.1. Materials

Locally sourced ordinary Portland cement type I-425 and hydrated lime respectively produced by Kordestan and Espandar Company were used as cementitious materials. Chemical composition and L.O.I of the binders are shown in Table 1. Hydrated lime or calcium hydroxide is decomposed into calcium oxide and water when it is heated up to 500° and therefore its L.O.I is significant.

Table 1. Chemical composition and physical properties of the cement and hydrated lime (%).

	CaO	SiO ₂	Fe ₂ O ₃	Al ₂ O ₃	MgO	SO ₃	Ca(OH) ₂	L.O.I
Cement	64.2	22.2	3.6	4.9	1.41	1.76	–	0.7
Hydrated lime	72.26	–	–	–	3.02	–	91.14	23.74

Locally sourced crushed coarse silica aggregate was used to make the pervious concretes without using fine aggregates. Physical properties of the aggregate were measured according to ASTM C127 and ASTM C566 and the results are shown in Table 2. Also grading curve of the aggregate, which was measured according to ASTM C136, and lower and upper limit of ASTM C33, size number of 67 (4.75–19.0 mm) for pervious concretes, are shown in Figure 1. It is clear that the grading curve of the aggregate that is close to the lower limit of the ASTM standard is appropriate to produce pervious concretes.

Renewable silica gel with capacity of 40 % of water absorption was used to absorb the evaporated water in the CO₂ chamber during the carbonation curing of the pervious concretes.

Table 2. Physical properties of the aggregates.

Physical property	Maximum nominal size (mm)	Water absorption (%)	Moisture content (%)	Specific gravity (t/m ³)
Coarse aggregate	19	1.8	0.9	2.57

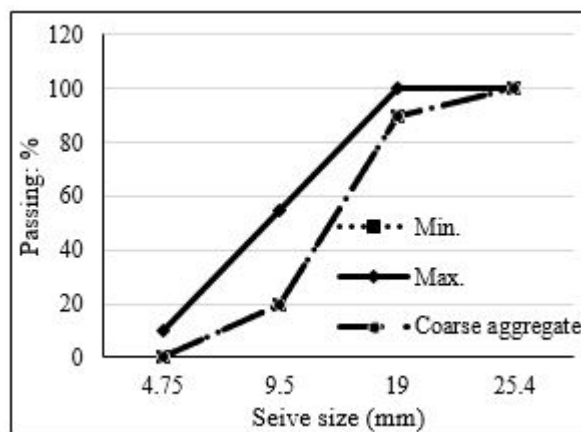


Figure 1. Grading curve of the coarse aggregate and lower and upper limits of ASTM C33.

2.2. Mix designs

Three mixtures containing 0, 15 and 30 % substitution of the hydrated lime were considered, where the mixture without substitution of hydrated lime was considered as the control one. The control mixture was designed using ACI 211.3R-02 [31] by assuming the compressive strength of 15 MPa and void content of 20 %, where water to cement ratio and the cement content were obtained equal to 0.35 and 350 kg/m³, respectively to obtain a desired pervious concrete. Slump of all mixtures were obtained lower than 20 mm and therefore there was no need to use superplasticizer. Water to binder ratio was kept constant in the mixtures. Details of the mixtures are summarized in Table 3.

Table 3. Details of mix designs.

	Cement (kg/m ³)	Hydrated lime (kg/m ³)	Hydrated lime (%)	Coarse aggregate (kg/m ³)
C1	350	0	0	1539
C2	297.5	52.5	15	1539
C3	245	105	30	1539

All mixtures were mixed for at least 3 minutes and the fresh concretes were then placed in the moulds ready to be compacted. Dimensions of the moulds which depend on the experiment type are mentioned in the next section. All mixtures were poured in three layers and each layer was gently compacted with 16 mm diameter of a bar in a same manner. Specimens were demoulded after 24 hours of moist curing and were then placed in a water bath (moist curing) or in the CO₂ chamber (CO₂ curing, see Figure 2). Considered specimens for CO₂ curing had been dried for 2 hours at a laboratory room before applying carbonation process to reduce their moisture content as the same as control room.

2.3. Experiments

Compressive and tensile strength, void content, permeability and CO₂ absorption capacity of the pervious concretes were investigated in this study, where the experiments were conducted at the age of 3, 7 and 28 days of moist curing and 1, 2, 4, 6, 12 and 24 hours of CO₂ curing. Two specimens were considered for each experiment and their average was reported. Compressive strength and void content testing were performed on 100×100×100 mm cubic specimens according to the BS 1881-116 test method. Void content of the specimens can be calculated using Equation (3), where W_1 is the oven dry weight of the specimen, W_2 is the weight of the immersed specimen in water, Vol is the volume of the specimen and ρ_w is the water density [32].

$$Vc(\%) = 1 - \left[\frac{W_1 - W_2}{\rho_w \times Vol} \right] \times 100. \quad (3)$$

Tensile strength testing was carried out on 100×200 mm cylindrical specimens according to ASTM C496. Water permeability of the 100×100 mm cylindrical specimens was measured according to Darcy's law. Permeability coefficient (k (cm/s)) of the specimens is calculated using Equation (4), where α and A (cm²) are the cross section area of the tube and the specimen, respectively, L (cm) is the specimen length, h_1 and h_2 (cm) are the water head in the tube before and after the measurements, respectively and t (s) is the time of head loss from h_1 to h_2 [33].

$$k = \frac{\alpha \cdot L}{A \cdot t} \times \ln \left(\frac{h_1}{h_2} \right). \quad (4)$$

CO₂ absorption capacity (COAC) test was conducted to explanation of the physical and mechanical properties of the CO₂ cured pervious concretes containing hydrated lime powders. No additional specimens were considered to COAC determination. First, the CO₂ cured cubic specimens were tested for the considered purpose and then were completely dried for 24 hours at the temperature of 105 °C. Then, some binder powder about 40 g were prepared by separation of the coarse aggregates from the specimens. Finally, COAC of the powders was determined by measuring the mass loss of the powder between 500 °C and 850 °C [14] and using Equation (5), where M_{850} and M_{500} are the powder mass at the correlated temperatures. Binder powders were placed into the oven and retained for 1 hour at the relevant temperature to achieve the constant mass.

$$COAC(\%) = \frac{M_{500} - M_{850}}{M_{500}} \times 100. \quad (5)$$

2.4. Carbonation curing of the specimens

The setup similar to the research of Kou et al [21] was used to apply CO₂ curing on the hydrated lime modified pervious concretes and schematic process of CO₂ curing is shown in Figure 2. To process the CO₂ curing, first the specimens were placed in the chamber and a vacuum was then applied to the chamber before

the CO₂ injection. Then, CO₂ gas having a purity of 97 % was used to simulate a point source. The pressure inside the chamber was kept constant equal to 1 MPa using a regulator to ensure a continuous supply of CO₂ gas. Temperature and humidity of the chamber were continuously controlled during the curing time using a group sensor. CO₂ curing time of the mixtures was considered equal to 1, 2, 4, 6, 12 and 24 hours. Then the CO₂ cured specimens were tested corresponding to the test program. Temperature of the chamber varied between 16–25 °C and the humidity of the chamber was controlled using silica gel. It should be noted that further silica gels were needed to absorb the evaporated water because of high porosity of the specimens.

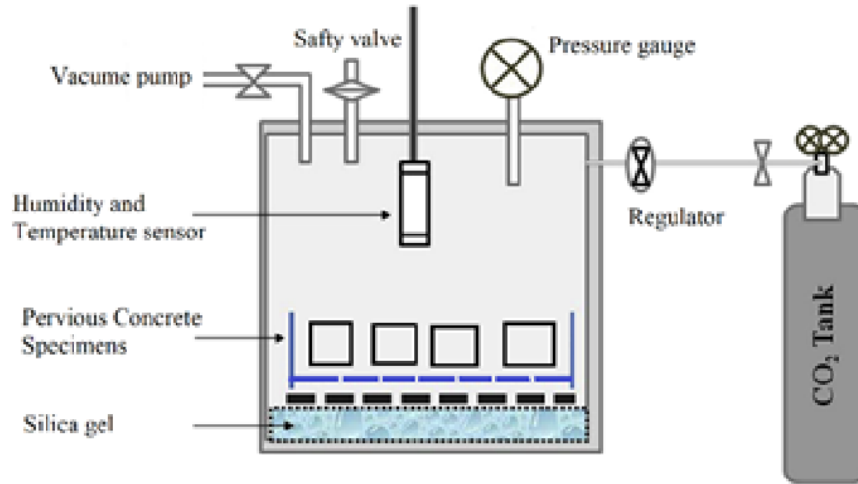


Figure 2. Schematic process of CO₂ curing similar to [21].

3. Results and discussion

3.1. Compressive strength

The results of the compressive strength tests are shown in Table 4 and Figures 3, 4. Table 4 shows the measured results and Figure 3 shows the compressive strength development over curing time in both cases of curing. Figure 4 shows the variations of relative compressive strength of CO₂ cured samples to the relevant 28 days compressive strength of moist cured samples.

Figure 3-a shows the control mixture was obtained the desired compressive strength after 28 days of moist curing. Also, mixtures covered about 50 % and 75 % of 28 days compressive strength after 3 and 7 days of moist curing, respectively. Figures 3-b and 4 show that the compressive strength increases with the increasing CO₂ curing time, where the increasing rate decreases with time in which the control mixture was obtained 45 % of 28 days moist cured compressive strength after 2 hours of CO₂ curing. This result is consistent with those found with the CO₂ curing of slag cement concrete [12]. These improvements are about 66 and 82 %, respectively after 6 and 12 hours of CO₂ curing. Also, the strength of C1 increased by 43 % and 74 % when CO₂ curing time was increased from 1 to 2 and 4 hours, respectively. These values have been reported about 16 % and 25 %, respectively for lightweight concretes [17]. Baojian et al. have reported 28 % and 42 % increasing in the strength when CO₂ curing time was increased from 6 to 12 and 24 hour [34], respectively for recycled aggregate concretes while these values are obtained about 24 % and 28 %, respectively in this study. Porous media of pervious concretes facilitates the penetration of CO₂ gas and therefore improvements are significant at the early ages of CO₂ curing in comparison with other concretes and consequently these improvements are declined for the later ages. Improvement of the compressive strength after 12 hours of CO₂ curing is negligible. Similar results were obtained for the concretes containing hydrated lime powder. Since the specimens are porous, CO₂ gas can simply be directed inside the specimens and the chemical reactions are completed. Therefore, first hours of initial CO₂ curing is more effective and can be simply used in the curing process of concretes.

Table 4. The results of the compressive strengths (MPa).

Mixture code	Moist curing (days)			CO ₂ Curing (hours)					
	3	7	28	1	2	4	6	12	24
C1	7.01	10.40	14.94	4.70	6.73	8.20	9.82	12.19	12.53
C2	8.04	11.52	15.58	5.03	7.25	9.18	10.05	12.68	12.94
C3	6.03	7.95	10.07	2.58	4.80	6.45	6.86	8.55	8.80

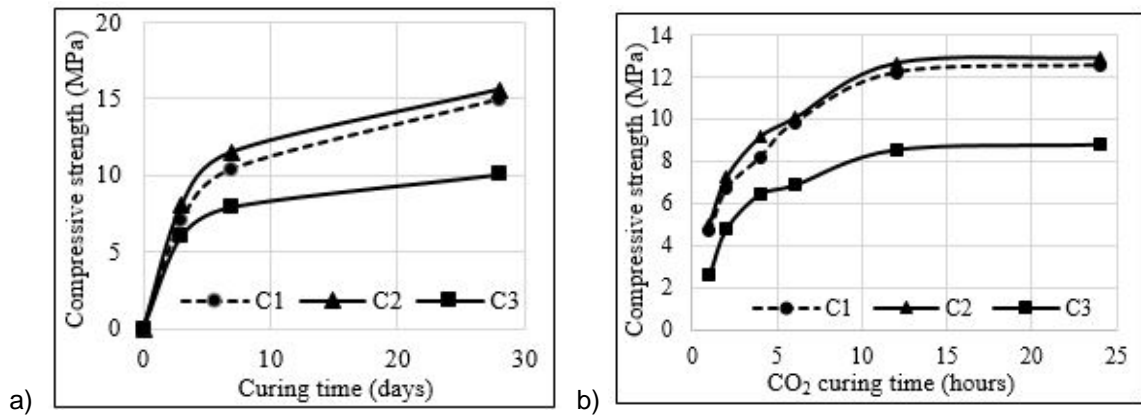


Figure 3. Compressive strength of the mixtures, a) moist cured and b) CO₂ cured.

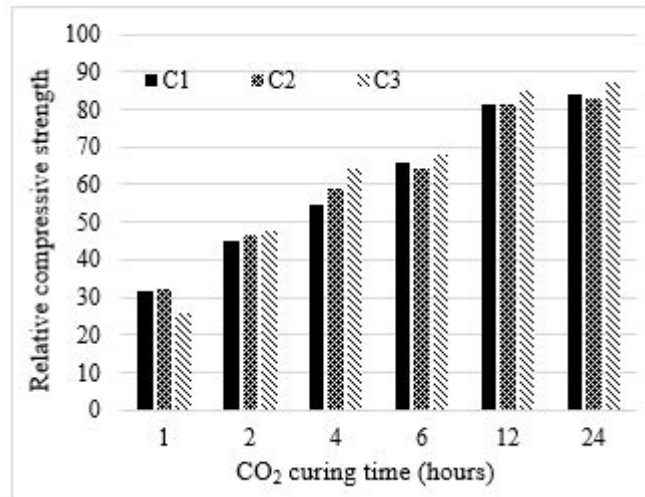


Figure 4. Relative compressive strength of CO₂ cured concretes to the relevant 28 days moist cured concretes.

Mixtures containing 15 % of hydrated lime showed higher compressive strength in both curing cases, but the mixture with substitution of 30 % hydrated lime showed lower compressive strength. This is due to in fact that the cementitious behavior of the hydrated lime is less than the cement and the 15 % substitution of the cement by hydrated lime make a dense structure of the binder. It is nevertheless predicted that the concretes containing 30 % hydrated lime absorb more CO₂ gas (see the COAC results), but their compressive strength are still lower than the control concretes.

3.2 Tensile strength

The results of tensile strengths tests are shown in Table 5. Results are similar to the compressive strength test results and the tensile strengths increase with increasing the curing time in both case of curing regimes. Table 6 present the tensile/compressive ratios and it is clear that the ratio decreased by increasing the curing time. The ratio was reached to 0.12–0.14 at the end of curing time. When the curing is continued, the compressive strength is increased more than tensile strength since the micro-cracks control the tensile strength [35] and therefore the tensile/compressive ratio is decreased.

Table 5. The results of the tensile strengths (MPa).

Mixture code	Moist curing (days)			CO ₂ Curing (hours)					
	3	7	28	1	2	4	6	12	24
C1	1.04	1.51	2.01	0.55	0.98	1.11	1.17	1.24	1.56
C2	1.05	1.43	2.00	0.72	0.90	0.99	1.22	1.30	1.55
C3	0.98	1.10	1.26	0.58	0.70	0.95	1.02	1.15	1.23

Table 6. Tensile/compressive ratio of the pervious concretes.

Mixture code	Moist curing (days)			CO ₂ Curing (hours)					
	3	7	28	1	2	4	6	12	24
C1	0.15	0.15	0.13	0.12	0.15	0.14	0.12	0.10	0.12
C2	0.13	0.12	0.13	0.14	0.12	0.11	0.12	0.10	0.12
C3	0.16	0.14	0.12	0.22	0.15	0.15	0.15	0.13	0.14

3.3. Void content

Void content of the specimens at the relevant curing times are shown in Table 7. It is clear that the void content of the concretes decreases with the increase of curing time in both cases of curing regimes and the reduction in Void content after 12 hours of CO₂ curing can be neglected similar to the compressive strength test results. Also, void contents of pervious concretes are controlled by aggregate composition rather than the porosity of the binder and therefore the variations of the void contents are ranged between 16.46–18.92 % according to Table 6.

Table 7. Void content of the pervious concretes (%).

Mixture code	Moist curing (days)			CO ₂ Curing (hours)					
	3	7	28	1	2	4	6	12	24
C1	18.64	17.80	17.09	17.65	17.50	17.40	16.81	16.63	16.57
C2	18.13	17.35	16.55	17.25	17.25	17.10	16.82	16.63	16.46
C3	18.92	18.31	17.43	18.80	18.34	17.68	17.47	17.12	17.10

Void contents of the mixtures are obtained in the predicted range of the mix designs, but the void content of the concretes containing hydrated lime after 12 hours of CO₂ curing is lower than that of the relevant mixtures after 28 days of moist curing. It is clarify that the mixtures containing hydrated lime have high ability to absorb further CO₂ gas. Figure 5 shows the relation between the compressive strength and void content in case of CO₂ curing, where the compressive strength is directly depended to the void content and it is increased by decreasing the void content.

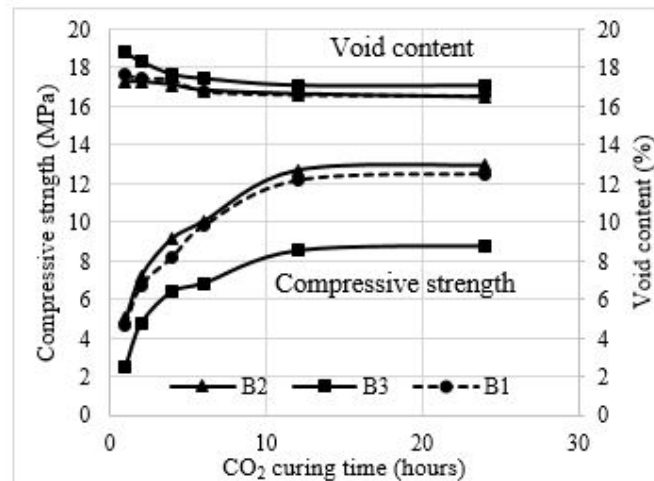


Figure 5. Validation of compressive strength and void content.

3.4. Water Permeability

Permeability coefficient of the specimens were calculated using Equation (5) and the results are summarized in Table 8. Water permeability of the concrete specimens depends on the connectivity of the pores and it is estimated that the permeability and void content are correlated and the results (see Figure 6) confirm such correlation and the permeability increases by increasing the void content. Also, permeability of the concretes decreases by increasing the curing time in both cases of curing.

Table 8. Permeability coefficients of the hydrated lime modified pervious concretes (cm/s).

Mixture code	Moist curing (days)			CO ₂ Curing (hours)					
	3	7	28	1	2	4	6	12	24
C1	6.63	5.37	5.30	7.00	6.84	6.48	5.60	5.06	5.08
C2	6.21	4.85	4.45	6.31	5.99	5.61	5.26	5.01	4.75
C3	7.21	6.82	6.48	8.37	7.30	6.77	6.72	6.50	6.50

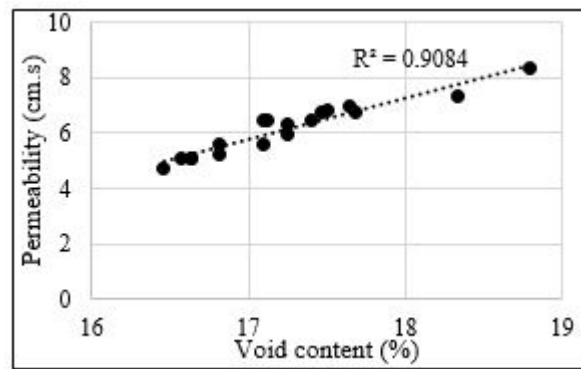


Figure 6. Correlation between permeability coefficient and void content.

3.5. CO₂ absorption capacity (COAC)

COAC of the concrete samples are shown in Figure 7, where the COAC of all mixtures was increased by increasing the curing time, but COAC at the first 2 hours of CO₂ curing covered about 70 % of COAC after 24 hours of CO₂ curing. Also, COAC was increased with the increasing of hydrated lime content. Moreover, concretes containing hydrated lime powders showed more potential to absorb CO₂ and the COAC of the hydrated lime modified concretes relatively is more than that of the control one, where the C2 and C3 were obtained 142 % and 192 % of COAC in comparison to the control one during the first hour of CO₂ curing. Figure 8, which shows the relative COAC of hydrated lime modified concretes to the relevant control one, clarify that the hydrated lime modified concretes have more potential than the control one despite of their low cement content. High volume of pores and high permeability coefficient of the concretes results in high permeation of CO₂ gas and high absorption of CO₂ during the initial time of curing. Also, high content of Ca(OH)₂ in the mixtures containing hydrated lime substitution increases the chemical reactions and lead to high carbonation content in the hydrated lime modified concretes. Moreover, increasing in the COAC after 12 hours of curing can be neglected.

Furthermore, COAC of the control mixture increased by 123 % and 167 % when CO₂ curing time was increased from 1 to 2 and 4 hours, respectively. These values have been reported about 5 % and 13 %, respectively for lightweight concretes [17]. Baojian et al. have reported 11 % and 33 % increasing in the COAC when CO₂ curing time was increased from 6 to 12 and 24 hour [34], respectively for recycled aggregate concretes while these values are about 5.9 % and 6.2 %, respectively in this study. Porous structure of pervious concretes simplifies the penetration of CO₂ gas into the concretes and therefore COACs are significant at the early ages of CO₂ curing in comparison with other concretes and consequently COACs are significantly reduced for the later ages.

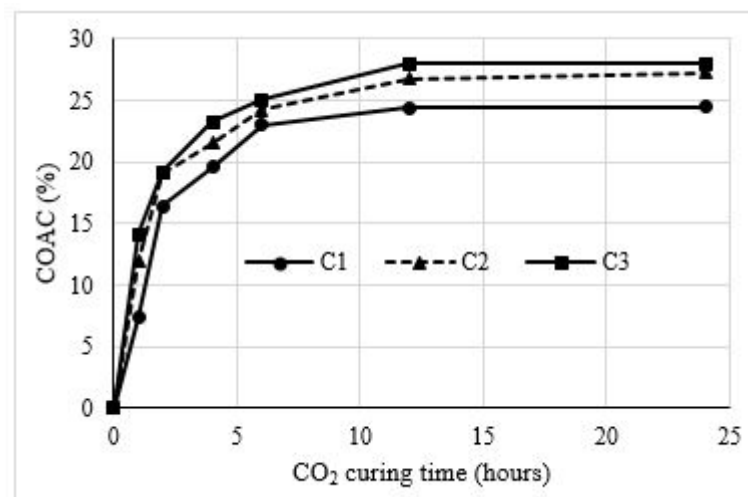


Figure 7. COAC of the pervious concrete over CO₂ curing time.

It is recommended to consider time of CO₂ curing of pervious concretes lower than 6 hours by respect of COAC result, while it is recommended about 12 hours of CO₂ curing by respect of obtaining mechanical properties.

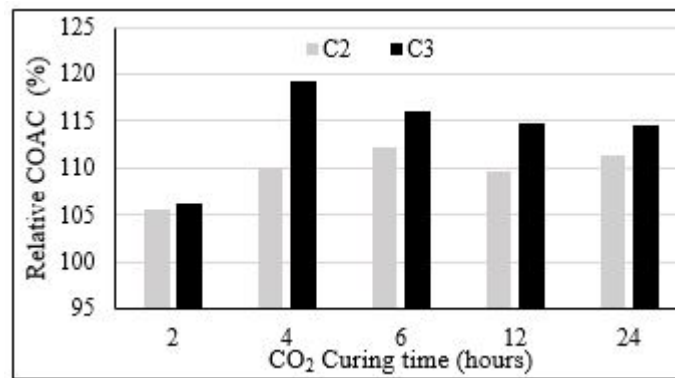


Figure 8. Relative COAC of the mixtures to the COAC of the control mixture.

4. Conclusion

An experimental program was conducted to investigate the effect of CO₂ curing on the physical and mechanical properties of pervious concretes with substitution of hydrated lime powders up to 30 % of cement. Moist curing and CO₂ curing were applied by up to 28 days and 24 hours, respectively. Also, CO₂ absorption capacity of the mixtures was investigated. The results of the conducted experiments are summarized as follows.

- 1- The major carbonation reactions of the pervious concretes were occurred in the first two hours of curing and then reactions were slowly continued up to 12 hours and then were approximately stopped.
- 2- Compressive strength of the CO₂ cured pervious concretes were obtained by up to 87 % of relevant compressive strength after 28 days of moist curing.
- 3- Hydrated lime substitution increases the CO₂ absorption capacity, where the 15–30 % replacement of hydrated lime increased the COAC up to 15 %.
- 4- Void content of the CO₂ cured hydrated lime modified concretes was less than the relevant void content of 28 days moist cured mixtures which confirms high CO₂ absorption capacity of the hydrated lime modified concretes.

5. Acknowledgments

The authors gratefully acknowledge University of Zanjan for support of this study as an MSc thesis.

References

1. Shao, Y., Mirza, M.S., Wu, X. CO₂ sequestration using calcium-silicate concrete [Online]. Canadian Journal of Civil Engineering. 2006. 33. Pp. 776–784. URL: <https://dx.doi.org/10.1139/05-105>.
2. Mourits, F. Capture and Sequestration of Greenhouse Gases in Canada (December 1997). 2012.
3. Penner, L., O'Connor, W.K., Dahlin, D.C., Gerdemann, S., Rush, G.E. Mineral carbonation: Energy costs of pretreatment options and insights gained from flow loop reaction studies. 3rd Annual Conference on Carbon Capture & Sequestration. 5(February)2004. Pp. 1–18.
4. Huijgen, W.J.J., Witkamp, G.J., Comans, R.N.J. Mineral CO₂ sequestration by steel slag carbonation. Environmental Science and Technology. 2005. 39(24). Pp. 9676–9682. DOI: 10.1021/es050795f.
5. Tu, Z., Shi, C., Farzadnia, N. Effect of limestone powder content on the early-age properties of CO₂-cured concrete. Journal of Materials in Civil Engineering. 2018. 30(8). Pp. 1–12. DOI: 10.1061/(ASCE)MT.1943-5533.0002232.
6. Young, J.F., Berger, R.L., Breese, J. Accelerated Curing of Compacted Calcium Silicate Mortars on Exposure to CO₂. Journal of the American Ceramic Society. 1974. 57(9). Pp. 394–397. DOI: 10.1111/j.1151-2916.1974.tb11420.x.
7. Berger, R.L., Young, J.F., Leung, K. Acceleration of Hydration of Calcium Silicates by Carbon Dioxide Treatment. Nature Physical Science. 1972. 240(97). Pp. 16–18. DOI: 10.1038/physci240016a0.
8. Goodbrake, C.J., Young, J.F., Berger, R.L. Reaction of Beta-Dicalcium Silicate and Tricalcium Silicate with Carbon Dioxide and Water Vapor. Journal of the American Ceramic Society. 1979. 62(3–4). Pp. 168–171. DOI: 10.1111/j.1151-2916.1979.tb19046.x.
9. Qin, L., Gao, X., Chen, T. Influence of mineral admixtures on carbonation curing of cement paste. Construction and Building Materials. 2019. 212. Pp. 653–662. DOI: 10.1016/j.conbuildmat.2019.04.033.
10. Ho, D.W.S., Lewis, R.K. Carbonation of concrete and its prediction. Cement and Concrete Research. 1987. 17(3). Pp. 489–504. DOI: 10.1016/0008-8846(87)90012-3.
11. Hermawan, S., Hata, T. Development technology of rapid production of high-strength cement-bonded particleboard by using gaseous or supercritical carbon dioxide curing. Proceedings of Inorganic-Bonded Wood and Fiber Composite Materials. 1998. Pp. 70–87.
12. Monkman, S., Shao, Y. Assessing the carbonation behavior of cementitious materials. Journal of Materials in Civil Engineering. 2006. 18(6). Pp. 768–776. DOI: 10.1061/(ASCE)0899-1561(2006)18:6(768).
13. Živica, V. Corrosion of reinforcement induced by environment containing chloride and carbon dioxide. Bulletin of Materials Science. 2003. 26(6). Pp. 605–608. DOI: 10.1007/BF02704323.
14. Montemor, M.F., Cunha, M.P., Ferreira, M.G., Simões, A.M. Corrosion behaviour of rebars in fly ash mortar exposed to carbon dioxide and chlorides. Cement and Concrete Composites. 2002. 24(1). Pp. 45–53. DOI: 10.1016/S0958-9465(01)00025-7.

15. Zhang, D., Shao, Y. Enhancing Chloride Corrosion Resistance of Precast Reinforced Concrete by Carbonation Curing. *ACI Materials Journal*. 2019. 116(3). DOI: 10.14359/51714461.
16. Zhan, B.J., Xuan, D.X., Zeng, W., Poon, C.S. Carbonation treatment of recycled concrete aggregate: Effect on transport properties and steel corrosion of recycled aggregate concrete. *Cement and Concrete Composites*. 2019. 104(May). Pp. 103360. DOI: 10.1016/j.cemconcomp.2019.103360.
17. Shi, C., Wu, Y. Studies on some factors affecting CO₂ curing of lightweight concrete products. *Resources, Conservation and Recycling*. 2008. 52(8–9). Pp. 1087–1092. DOI: 10.1016/j.resconrec.2008.05.002.
18. Shao, Y.; and Shi, C. Carbonation curing for making concrete products—an old concept and a renewed interest. 6th International Symposium on Cement and Concrete. 2006. Pp. 823–830.
19. Zhan, B.J., Xuan, D.X., Poon, C.S., Shi, C.J. Effect of curing parameters on CO₂ curing of concrete blocks containing recycled aggregates. *Cement and Concrete Composites*. 2016. 71. Pp. 122–130. DOI: 10.1016/j.cemconcomp.2016.05.002.
20. Zhan, B.J., Poon, C.S., Shi, C.J. Materials characteristics affecting CO₂ curing of concrete blocks containing recycled aggregates. *Cement and Concrete Composites*. 2016. 67. Pp. 50–59. DOI: 10.1016/j.cemconcomp.2015.12.003.
21. Kou, S.C., Zhan, B.J., Poon, C.S. Use of a CO₂ curing step to improve the properties of concrete prepared with recycled aggregates. *Cement and Concrete Composites*. 2014. 45. Pp. 22–28. DOI: 10.1016/j.cemconcomp.2013.09.008.
22. Ahmad, S., Assaggaf, R.A., Adekunle, S.K., Al-Amoudi, O.S.B., Maslehuddin, M., Ali, S.I. Influence of accelerated carbonation curing on the properties of self-compacting concrete mixtures containing different mineral fillers. *European Journal of Environmental and Civil Engineering*. 2019. 0(0). Pp. 1–18. DOI: 10.1080/19648189.2019.1649197.
23. Hasegawa, L.I.I. Carbonation curing and performance of pervious concrete using Portland limestone cement. McGill, 2011.
24. Sidhu, G.S. Effect of Accelerated Carbonation Curing On Properties of Pervious Concrete: An Effective Way of CO₂ Sequestration and Water Conservation. Thapar Institute, 2019.
25. Lian, C., Zhuge, Y., Beecham, S. The relationship between porosity and strength for porous concrete. *Construction and Building Materials*. 2011. 25(11). Pp. 4294–4298. DOI: 10.1016/j.conbuildmat.2011.05.005.
26. Aamer Rafique Bhutta, M., Hasanah, N., Farhayu, N., Hussin, M.W., Tahir, M.B.M., Mirza, J. Properties of porous concrete from waste crushed concrete (recycled aggregate). *Construction and Building Materials*. 2013. 47. Pp. 1243–1248. DOI: 10.1016/j.conbuildmat.2013.06.022.
27. De Solomihac, H., Videla, C., Fernández, B., Castro, J. Porous concrete mixtures for pervious urban pavements. *Materiales de Construccion*. 2007. 57(287). Pp. 23–36.
28. Shen, W., Shan, L., Zhang, T., Ma, H., Cai, Z., Shi, H. Investigation on polymer-rubber aggregate modified porous concrete. *Construction and Building Materials*. 2013. 38. Pp. 667–674. DOI: 10.1016/j.conbuildmat.2012.09.006.
29. Bhutta, M.A.R., Tsuruta, K., Mirza, J. Evaluation of high-performance porous concrete properties. *Construction and Building Materials*. 2012. 31. Pp. 67–73. DOI: 10.1016/j.conbuildmat.2011.12.024.
30. Park, S.B., Seo, D.S., Lee, J. Studies on the sound absorption characteristics of porous concrete based on the content of recycled aggregate and target void ratio. *Cement and Concrete Research*. 2005. 35(9). Pp. 1846–1854. DOI: 10.1016/j.cemconres.2004.12.009.
31. ACI 211.3R. Guide for Selecting Proportions for No-Slump Concrete. 211.3R2002.
32. Park, S.B., Tia, M. An experimental study on the water-purification properties of porous concrete. *Cement and Concrete Research*. 2004. 34(2). Pp. 177–184. DOI: 10.1016/S0008-8846(03)00223-0.
33. Neithalath, N., Weiss, J., Olek, J. Characterizing Enhanced Porosity Concrete using electrical impedance to predict acoustic and hydraulic performance. *Cement and Concrete Research*. 2006. 36(11). Pp. 2074–2085. DOI: 10.1016/j.cemconres.2006.09.001.
34. Baojian, Z., Chisun, P., Caijun, S. CO₂ curing for improving the properties of concrete blocks containing recycled aggregates. *Cement and Concrete Composites*. 2013. 42. Pp. 1–8. DOI: 10.1016/j.cemconcomp.2013.04.013.
35. Mehta, P.K., Monteiro, P.J.M. *Concrete: Microstructure, Properties, and Materials*. 3rd ed. McGraw-Hill. New York, 2005.

Contacts:

Hamid Rahmani, +982433054057; hrahmani@znu.ac.ir

Mohammad Montazer Gheib, +989369635763; mohammadmontazer.ci@gmail.com